

RILSAMID®

AZM 30 O TLD

ISO 16396 - PA12 , GF30, M1GHLR, C16-070

Rilsamid® AZM 30 O TLD resin is a fiberglass reinforced polyamide. This natural grade is designed for injection moulding.

This grade is also available in green (Rilsamid® AZM 30 Green 56827 TLD resin) and grey (Rilsamid® AZM 30 Grey 632 TLD resin).

PROPERTIES	DRY / COND	UNIT	TEST STANDARD
RHEOLOGICAL PROPERTIES			
Melt Volume-Flow Rate	12 / *	cm ³ /10 min	ISO 1133
Temperature	235 / *	°C	-
	455 / *	°F	-
Load	5 / *	kg	-
	11 / *	lb	-
Melt Flow Rate	≥12.8	g/10min	ASTM D1238
MECHANICAL PROPERTIES			
Tensile Modulus	6900 / 6500	MPa	ISO 527-1/-2
	1E6 / 943000	psi	
Yield Stress	127 / 115	MPa	ISO 527-1/-2
	18400 / 16700	psi	
Yield Strain	4 / 4	%	ISO 527-1/-2
Stress at Break	122 / 110	MPa	ISO 527-1/-2
	17700 / 16000	psi	
Strain at Break	5 / 6	%	ISO 527-1/-2
Charpy Impact Strength, +23°C	85 / 88	kJ/m ²	ISO 179/1eU
	40.4 / 41.9	ftlb/in ²	
Charpy Impact Strength, -30°C	96 / 93	kJ/m ²	ISO 179/1eU
	45.7 / 44.2	ftlb/in ²	
Charpy Notched Impact Strength, +23°C	23 / 22	kJ/m ²	ISO 179/1eA
	10.9 / 10.5	ftlb/in ²	
Charpy Notched Impact Strength, -30°C	15 / 16	kJ/m ²	ISO 179/1eA
	7.14 / 7.61	ftlb/in ²	
THERMAL PROPERTIES			
Melting Temperature, 10°C/min	179 / *	°C	ISO 11357-1/-3
Temp. of Deflection Under Load, 1.80 MPa	160 / *	°C	ISO 75-1/-2
	320 / *	°F	

Arkema France - A French "société anonyme", registered in the Nanterre (France) Trade and Companies Register under the number 319 632 790 SDC/11-2018
Source: automatically generated TDS from Material Database on 20-02-2024

RILSAMID[®]

AZM 30 O TLD

Temp. of Deflection Under Load, 0.45 MPa	175 / *	°C	ISO 75-1/-2
	347 / *	°F	
Vicat Softening Temperature, 50°C/h 50N	165 / *	°C	ISO 306
	329 / *	°F	
Coeff. of Linear Thermal Expansion, parallel	50 / *	E-6/K	ISO 11359-1/-2
Thermal Decomposition TGA, in air	224	°C	1% wt. loss
	436	°F	
Thermal Decomposition TGA, in nitrogen	222	°C	1% wt. loss
	431	°F	
ELECTRICAL PROPERTIES			
Relative Permittivity, 100Hz	4 / -	-	IEC 60250
Relative Permittivity, 1MHz	4 / -	-	IEC 60250
Dissipation Factor, 100Hz	752 / -	E-4	IEC 60250
Dissipation Factor, 1MHz	251 / -	E-4	IEC 60250
Volume Resistivity	- / 1E11	Ohm* m	IEC 62631-3-1
Surface Resistivity	* / 1E14	Ohm	IEC 62631-3-2
Dielectric (Electric) Strength	- / 45	kV/mm	IEC 60243-1
	- / 1140	kV/in	
Comparative Tracking Index	* / 600	-	IEC 60112
OTHER PROPERTIES			
Water Absorption, 23°C, immersion, equilibrium	1.2 / *	%	ISO 62
Humidity Absorption, 23°C, RH50%, equilibrium	0.6 / *	%	ISO 62
Density	1230 / 1230	kg/m ³	ISO 1183
	1.23 / 1.23	g/cm ³	

PACKAGING:&NBSP;

This grade is delivered dried in sealed packaging (25 kg bags) ready to be processed

SHELF LIFE:

Two years from the delivery.


For any use above this limit please refer to our technical services.

RILSAMID[®]


AZM 30 O TLD

DIAGRAMS


VISCOSITY-SHEAR RATE

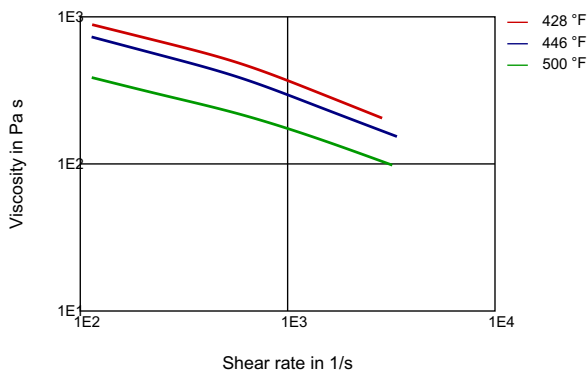


SHEARSTRESS-SHEAR RATE

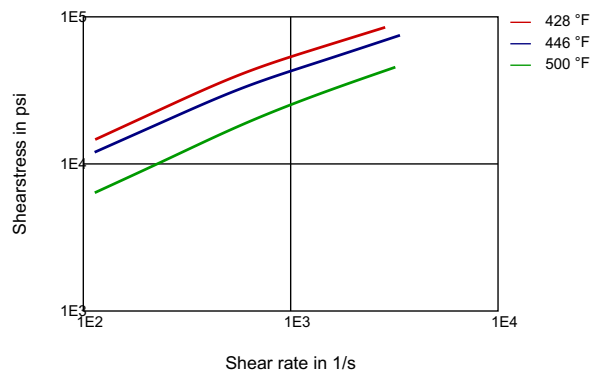

STRESS-STRAIN (ISOCHRONOUS) 73°F

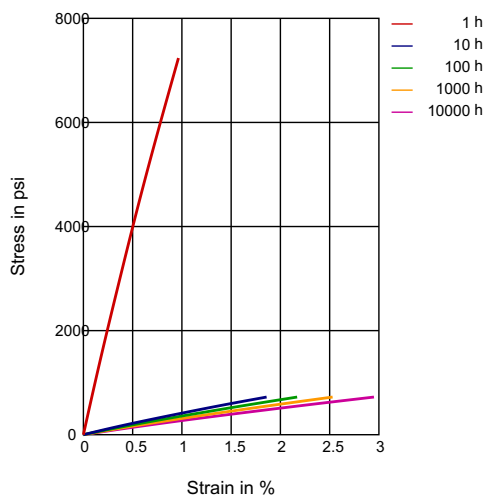

CREEP MODULUS-TIME 73°F

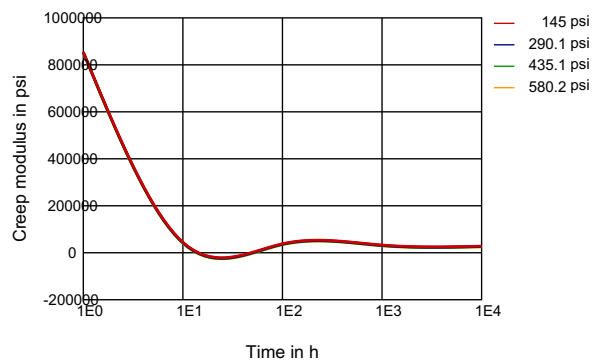

Processing conditions:

- Typical melt temperature (Min / Recommended / Max) : 250°C / 265°C / 280°C.
- Typical mold temperature : 40 – 90°C.
- Drying time and temperature (only necessary for bags opened for more than two hours) : 4-8 hours at 80-90°C.

RILSAMID[®]

AZM 30 O TLD

PROCESSING Injection Molding	Headquarters: Arkema France 420 rue d'Estienne d'Orves 92705 Colombes Cedex France T +33 (0)1 49 00 80 80 hpp.arkema.com Arkema Inc. – High Performance Polymers 900 First Avenue King of Prussia, PA 19406 Tel.: +1 610 205 7000 hpp.arkema.com
DELIVERY FORM Pellets	
ADDITIVES Release agent	
SPECIAL CHARACTERISTICS Heat Stabilized, Light Stabilized	
REGIONAL AVAILABILITY North America, Europe, Asia Pacific, South and Central America, Near East/Africa	

The statements, technical information and recommendations contained herein are believed to be accurate as of the date hereof. Since the conditions and methods of use of the product and of the information referred to herein are beyond our control, ARKEMA expressly disclaims any and all liability as to any results obtained or arising from any use of the product or reliance on such information; NO WARRANTY OF FITNESS FOR ANY PARTICULAR PURPOSE, WARRANTY OF MERCHANTABILITY OR ANY OTHER WARRANTY, EXPRESSED OR IMPLIED, IS MADE CONCERNING THE GOODS DESCRIBED OR THE INFORMATION PROVIDED HEREIN. The information provided herein relates only to the specific product designated and may not be applicable when such product is used in combination with other materials or in any process. The user should thoroughly test any application before commercialization. Nothing contained herein constitutes a license to practice under any patent and it should not be construed as an inducement to infringe any patent and the user is advised to take appropriate steps to be sure that any proposed use of the product will not result in patent infringement.